

INCOLOY® alloy 907 (UNS N19907) is a nickel-iron-cobalt alloy having high strength along with a low coefficient of thermal expansion. The alloy is strengthened by age-hardening heat treatments. Table 1 lists the chemical composition of the alloy.

The combination of low expansion and high strength makes INCOLOY alloy 907 useful for gas-turbine components. The low expansion enables closer control of clearances and tolerances for greater fuel efficiency. The high strength makes possible higher strength-to-density ratios for lower weight in aircraft engines. For those reasons, INCOLOY alloy 907 is used for gas-turbine seals, shafts, casings, and other structural parts.

The properties of INCOLOY alloy 907 are attractive for other applications including instrumentation, glass-to-metal sealing, ceramic-molding dies, and electricity generation.

Physical Properties

Some physical properties of INCOLOY® alloy 907 are listed in Table 2. The values were determined for age-hardened material. Values for modulus of elasticity were determined dynamically and were used to calculate Poisson's ratio. Values were determined at room temperature unless otherwise noted.

The composition of INCOLOY alloy 907 is designed to provide a low coefficient of thermal expansion that remains constant over a broad temperature range. As shown in Figure 1, coefficient of expansion is typically 4.0 to $4.5 \times 10^{-6}/^{\circ}\text{F}$ (7.2 to $8.1 \times 10^{-6}/^{\circ}\text{C}$) at temperatures to about 800°F (430°C). The expansion rate is about half that of other alloys of comparable strength. Further, the expansion characteristics of alloy 907 are highly reproducible after both static and cyclic exposure to temperature.

INCOLOY alloy 907 has a nearly constant modulus of elasticity over temperature ranges from the cryogenic region to 1200°F (650°C). Table 3 lists modulus values at various temperatures. Testing was done on age-hardened material using a dynamic method.

The combination of low expansion and constant modulus makes INCOLOY alloy 907 highly resistant to thermal fatigue and thermal shock. The alloy's high-temperature performance is also enhanced by relatively high thermal conductivity.

Table 1 - Limiting Chemical Composition, %

Nickel	35.0-40.0
Cobalt.....	12.0-16.0
Iron	Balance*
Niobium.....	4.3-5.2
Titanium.....	1.3-1.8
Aluminum.....	0.2 max.
Silicon.....	0.07-0.35

*Reference to the 'balance' of an alloy's composition does not guarantee this is exclusively of the element mentioned, but that it predominates and others are present only in minimal quantities.

Table 2 - Physical & Thermal Properties

Density, lb/in ³	0.301
Mg/cm ³	8.33
Melting Range, $^{\circ}\text{F}$	2440-2550
$^{\circ}\text{C}$	1335-1400
Specific Heat, Btu/lb- $^{\circ}\text{F}$	0.103
J/kg- $^{\circ}\text{C}$	431
Curie Temperature, $^{\circ}\text{F}$	750-850
$^{\circ}\text{C}$	400-455
Thermal Conductivity at 200°F (93°C),	
Btu-in/ft ² -h- $^{\circ}\text{F}$	108.5
W/m- $^{\circ}\text{C}$	15.6
Electrical Resistivity, ohm circ mil/ft.....	419
$\mu\Omega\text{-m}$	0.697
Young's Modulus, 10^3 ksi	23.9
GPa.....	165
Shear Modulus, 10^3 ksi	8.8
GPa.....	61
Poisson's Ratio.....	0.36

Table 3 - Modulus of Elasticity of Age-Hardened ^a
INCOLOY alloy 907

Temperature		Young's Modulus		Shear Modulus		Poisson's Ratio
$^{\circ}\text{F}$	$^{\circ}\text{C}$	10^3 ksi	GPa	10^3 ksi	GPa	
70	21	23.9	165	8.8	61	0.36
200	93	23.8	164	8.7	60	0.37
400	204	23.8	164	8.7	60	0.37
600	316	24.0	165	8.9	61	0.35
700	371	24.1	166	9.0	62	0.34
800	427	24.3	168	9.1	63	0.34
900	482	24.2	167	9.0	62	0.34
1000	538	23.9	165	8.8	61	0.36
1200	649	23.0	159	8.4	58	0.36
1400	760	21.8	150	8.0	55	0.36
1600	871	20.5	141	7.4	51	0.39

^aAge hardened for rupture-limited applications



INCOLOY® alloy 907

Mechanical Properties

In the age-hardened condition, INCOLOY® alloy 907 has high mechanical properties. For example, when heat treated for optimum tensile properties, INCOLOY alloy 907 has yield and tensile strengths similar to those of INCONEL® alloy 718.

INCOLOY alloy 907 normally receives one of two heat treatments, depending on whether the strength requirements of the application are tensile limited or rupture limited. For tensile-limited applications, the age-hardening treatment is:

1325°F (720°C)/8 h, furnace cool at 100°F (55°C)/h to 1150°F (620°C)/8 h, air cool.

For rupture-limited applications, the treatment is:

1425°F (775°C)/12 h, furnace cool at 100°F (55°C)/h to 1150°F (620°C)/8 h, air cool.

Before either age-hardening treatment, the alloy is given a solution anneal of 1800°F (980°C)/1 h, air cool. Heat treatment of INCOLOY alloy 907 is covered by a U.S. patent.

Table 4 shows tensile properties of INCOLOY alloy 907 at room temperature and various elevated temperatures. The material tested had been given the heat treatment for tensile-limited applications. Tensile properties of material heat treated for rupture-limited applications are listed in Table 5. All tensile testing was in the long-transverse direction using specimens from 5-in × 0.75-in (127-mm × 19-mm) flat bars.

Stress-rupture strength of material given the heat treatment for rupture-limited applications is given in Figure 2. The test orientation of the specimens was transverse to the hot-rolling direction used in production of the bar stock.

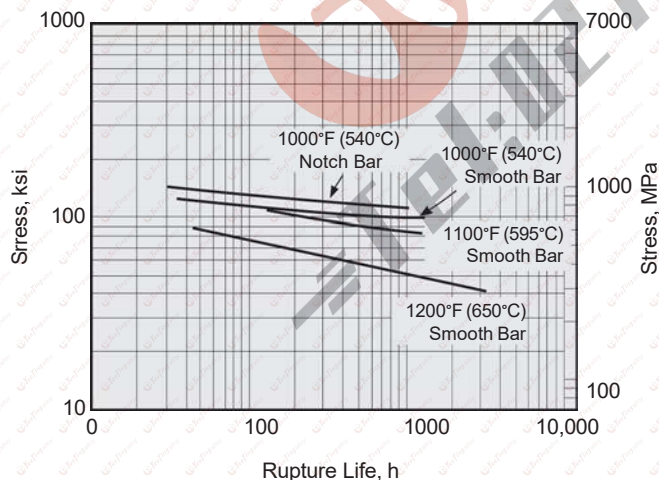


Figure 2. Rupture strength of age-hardened INCOLOY alloy 907. Notch-bar specimens: $K_t = 2.0$. Test material was given the heat treatment for rupture-limited applications.

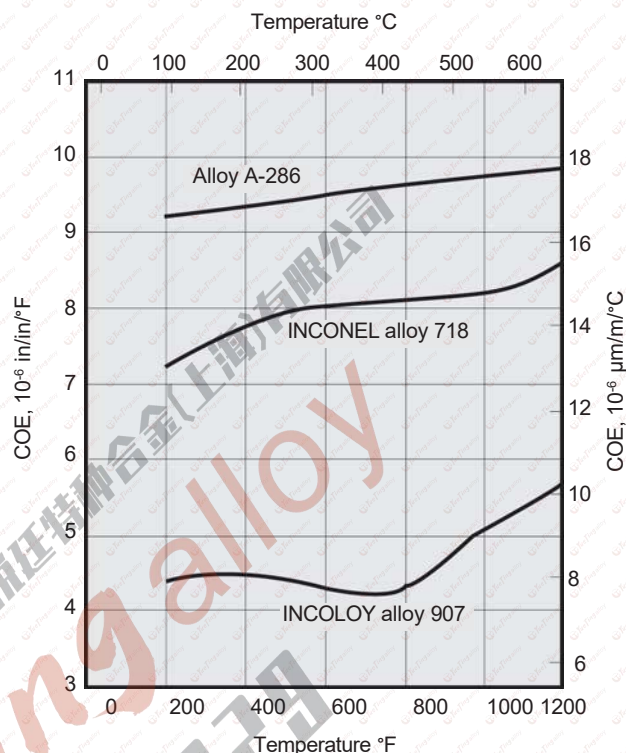


Figure 1. Coefficients of expansion of INCOLOY alloy 907 and other high-strength alloys. Alloy 907 was heat treated for rupture-limited applications.

Table 4 - Tensile Properties of Age-Hardened^a INCOLOY alloy 907

Temperature		Yield Strength (0.2% Offset)		Tensile Strength		Elongation, %	Reduction of Area, %
°F	°C	ksi	MPa	ksi	MPa		
70	20	162.5	1120	194.5	1341	15.0	36.5
800	427	142.4	982	168.3	1160	14.9	40.7
1000	538	137.5	948	164.3	1133	13.8	42.2
1200	649	126.2	870	151.2	1043	10.2	26.8
1400	760	82.0	565	93.9	647	20.9	52.0

^aAge hardened for tensile-limited applications

Table 5 - Tensile Properties of Age-Hardened^a INCOLOY alloy 907

Temperature		Yield Strength (0.2% Offset)		Tensile Strength		Elongation, %	Reduction of Area, %
°F	°C	ksi	MPa	ksi	MPa		
70	20	128.5	886	175.5	1210	16.0	25.0
800	427	105.1	725	154.8	1067	16.6	32.6
1000	538	105.5	727	150.2	1036	15.8	38.0
1200	649	98.7	681	136.5	941	19.8	42.2
1400	760	63.5	438	77.4	534	31.5	70.2

^aAge hardened for rupture-limited applications

Microstructure

The heat treatment given INCOLOY alloy 907 for rupture-limited applications is an over-aging treatment designed to optimize the alloy's notch-bar rupture strength. The heat treatment causes localized precipitation, both intergranular and intragranular, of $\text{Ni}_3(\text{Nb}, \text{Ti})$ phase. The acicular, hexagonal phase is referred to as epsilon or epsilon double-prime.

Corrosion Resistance

INCOLOY alloy 907 contains no chromium because the presence of that element would increase thermal expansion. The absence of chromium, however, makes the alloy more susceptible to oxidation in high-temperature atmospheres. In some applications, INCOLOY alloy 907 may require a protective coating to prevent excessive oxidation. Figure 3 compares INCOLOY alloy 907 with INCONEL® alloy 718 (19% chromium) in a cyclic oxidation test at 1200°F (650°C).

A characteristic of INCOLOY alloy 907 is that unlike other alloys of comparable strength, it has good resistance to embrittlement in high-pressure hydrogen.

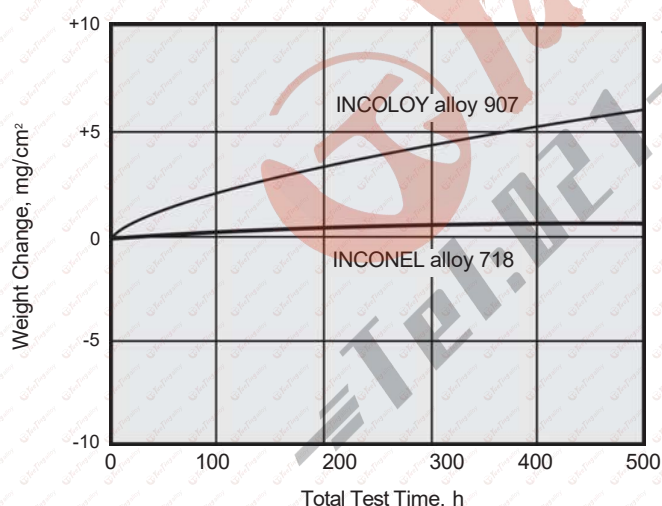


Figure 3 - Resistance to cyclic oxidation at 1200°F (650°C). Cycles consisted of 15 minutes of exposure to temperature and 5 minutes of cooling in air.

Fabrication

HOT WORKING

INCOLOY alloy 907 has hot-working characteristics similar to those of INCONEL alloy 718. The temperature range for hot working is 1650°F to 2100°F (900°C to 1150°C). Some hot working should be done at 1850°F to 1950° (1010°C to 1065°C) to refine the grain structure. A final reduction of at least 20% at a temperature under 1800°F (980°C) is needed for optimum mechanical properties.

MACHINING

INCOLOY alloy 907 is machined by conventional practices for high-strength materials. In machinability tests, INCOLOY alloy 907 is similar to INCONEL alloy 718. Best results are obtained when machining is done on annealed material. Tooling and procedures should be those given for Group D-2 alloys in the publication "Machining" on the website www.yttzhj.com.

WELDING

INCOLOY alloy 907 has good weldability similar to that of INCONEL alloy 718. The alloy has been successfully welded by gas-metal-arc, gas-tungsten-arc, and electron-beam processes. Matching-composition filler metal and INCONEL Filler Metal 718 have been used.

Available Products

INCOLOY alloy 907, designated UNS N19907, is available as round bar and forging stock. Further information on availability may be obtained from the nearest Special Metals office.

Publication Number SMC-098

Copyright © Special Metals Corporation, 2004 (Sept 04)

INCOLOY and INCONEL are trademarks of the Special Metals Corporation group of companies.

The data contained in this publication is for informational purposes only and may be revised at any time without prior notice. The data is believed to be accurate and reliable, but Special Metals makes no representation or warranty of any kind (express or implied) and assumes no liability with respect to the accuracy or completeness of the information contained herein. Although the data is believed to be representative of the product, the actual characteristics or performance of the product may vary from what is shown in this publication. Nothing contained in this publication should be construed as guaranteeing the product for a particular use or application.